

# **Modern Environmental Science and Engineering**

Volume 8, Number 3, March 2022



### **Editorial Board Members:**

Prof. Shin-Jye Liang (Taiwan)  
Prof. László Tóth (Hungary)  
Dr. Pierantonio De Luca (Italy)  
Prof. Teodor Rusu (Romania)  
Dr. Ahmed Moustafa Ahmed Moussa (Egypt)  
Prof. Nikolina Tzvetkova (Bulgaria)  
Dr. Riccardo Buccolieri (Italy)  
Prof. Ajay Kumar Mishra (South Africa)  
Dr. Saleh Almogrin (Saudi Arabia)  
Prof. Carlos Alberto Carvalho Castro (Brazil)  
Prof. Muzher Mahdi Ibrahim (Iraq)  
Prof. Abdelazim Mohamed Abdelhamid Negr (Egypt)  
Prof. Carlos Alberto Carvalho Castro (Brazil)  
Prof. Cecilia Lezama Escalante (México)  
Prof. Juchao Yan (USA)  
Prof. Levent Bat (Turkey)  
Prof. Kristaq BERXHOLI (Albania)  
Prof. Bakenaz A. Zeidan (Egypt)  
Prof. Juraj Králik (Slovak)  
Prof. Wail Nourildean Al Rifai (Jordan)  
Prof. Heng Zhang (Taiwan)  
Assist. Prof. Michela Longo (Italy)  
Prof. Mona Nabil ElHazeek (Egypt)  
Prof. Fares D Alsewailem (Saudi Arabia)  
Prof. Miklas Scholz (Sweden)  
Prof. Abdulrazag Y. Zekri (UAE)  
Prof. Maria Ananiadou – Tzimopoulou (Greece)  
Prof. Tetsuya Hiraishi (Japan)  
Prof. Alaeddin BOBAT (Turkey)  
Prof. Ying I. Tsai (Taiwan)  
Prof. Michela Longo (Italy)  
Prof. Mona Nabil ElHazeek (Egypt)  
Prof. Fares D Alsewailem (Saudi Arabia)  
Prof. Miklas Scholz (Sweden)  
Prof. Abdulrazag Y. Zekri (UAE)  
Prof. Maria Ananiadou – Tzimopoulou (Greece)  
Prof. Alaeddin BOBAT (Turkey)  
Prof. Essam E. Khalil (Egypt )  
Prof. Ying I. Tsai (Taiwan)  
Prof. Antonio Formisano (Italy)  
Prof. Erivelto Luís de Souza (Brazil)  
Prof. Kim Choon Ng (Saudi Arabia)  
Prof. Adilson Costa Macedo (Brazil)  
Prof. Dr. Andrey N. Dmitriev (Russia)  
Prof. Abdelaziz Khlaifat (UAE)  
Prof. Maria Paola Gatti (Italy)  
Prof. Viacheslav Manukalo (Ukraine)  
Prof. Elena Mussinelli (Italy)  
Prof. George Papadakis (Greece)  
Prof. INOM NORMATOV (Tajikistan)  
Asst Prof. Dr. Mustafa Toker (Turkey)  
Prof. Shouji Usuda (Japan)

### **Copyright and Permission:**

Copyright©2022 by Modern Environmental Science and Engineering, Academic Star Publishing Company and individual contributors. All rights reserved. Academic Star Publishing Company holds the exclusive copyright of all the contents of this journal. In accordance with the international convention, no part of this journal may be reproduced or transmitted by any media or publishing organs (including various websites) without the written permission of the copyright holder. Otherwise, any conduct would be considered as the violation of the copyright. The contents of this journal are available for any citation. However, all the citations should be clearly indicated with the title of this journal, serial number and the name of the author.

### **Subscription Information:**

Price: US\$500/year (print)

Those who want to subscribe to our journal can contact: [finance@academicstar.us](mailto:finance@academicstar.us).

### **Peer Review Policy:**

Modern Environmental Science and Engineering (ISSN 2333-2581) is a refereed journal. All research articles in this journal undergo rigorous peer review, based on initial editor screening and anonymous refereeing by at least two anonymous referees. The review process usually takes 2-4 weeks. Papers are accepted for publication subject to no substantive, stylistic editing. The editor reserves the right to make any necessary changes in the papers, or request the author to do so, or reject the paper submitted.

### **Database Index:**

Modern Environmental Science and Engineering (ISSN 2333-2581) is indexed by SSRN, CrossRef, Google Scholar and Ulrich now.

### **Contact Information:**

Manuscripts can be submitted to: [mese@academicstar.us](mailto:mese@academicstar.us), [environment@academicstar.us](mailto:environment@academicstar.us) or [service@academicstar.us](mailto:service@academicstar.us). Constructions for Authors and Submission Online System are available at our website: <http://www.academicstar.us/onlineupload.asp?shaction=show>.

**Address:** 1820 Avenue M Suite #1068, Brooklyn, NY 11230

**Tel:** 347-566-2153, **Fax:** 646-619-4168

**E-mail:** [mese@academicstar.us](mailto:mese@academicstar.us), [environment@academicstar.us](mailto:environment@academicstar.us)



# Modern Environmental Science and Engineering

Volume 8, Number 3, March 2022

## Contents

### Technical Papers

- 141 **Performance of Recycled Materials in Pavement Subbase After 4 Years in a Hot Desert Climate**  
*Khaled E Hassan, Murray Reid, and Mohammed bin Saif Al-Kuwari*
- 152 **Airports as Actors in the in the Transformation of the Environment and Hydrological Environment**  
*Teresita Cano Ricárdez, Cuauhtémoc Rafael Gonzalez García, and Vanessa Mendoza Nila*
- 163 **Sustainability in Creative Projects: Biophilia Contributions**  
*Alice Araujo Marques de Sá, and Dianne Magalhães Viana*
- 173 **Growth Performance of Life (*Trichomycterus punctulatus*) Raised in an Intensive Recirculating Aquaculture System**  
*Concepción Santiago Cubas, and Concepción Paredes Gil*
- 180 **Analysis on the Impact of Typhoon HAITANG on Heilongjiang Province**  
*Xiaoxue Wang, Jiaying Zhao, Li Ren, Meiling Zhao, and Ning Zhao*
- 186 **Growth Performance of Life (*Trichomycterus punctulatus*) Raised in an Intensive Recirculating Aquaculture System**  
*Segundo Juan López Cubas, María V. Lora Vargas, and Dreime Toro Montenegro*
- 195 **Canteiro Kit: Ecological Thinking With Science**  
*Kelly Beatriz Danelon, Julia Alves Pennachin, Zuleide de Toledo Trevisan, Rogéria Cancilieri, Sueli Alexandre Bassetti, Sandra de Fatima Cruz, Ana Maria Meira de Lello, Fernando Campos Mendonça, and Rosebelly Nunes Marques*



# Performance of Recycled Materials in Pavement Subbase After 4 Years in a Hot Desert Climate

Khaled E Hassan<sup>1</sup>, Murray Reid<sup>2</sup>, and Mohammed bin Saif Al-Kuwari<sup>3</sup>

1. Infrastructure Research & Development, Doha, Qatar

2. Infrastructure Research and Development, Glasgow, UK

3. Ministry of Municipality and Environment, Doha, Qatar

**Abstract:** The paper presents a field investigation on the use of alternative subbase materials from excavation and demolition waste in subbase applications in a desert area. A road trial was constructed with three subbase sections, comprising excavation waste (EW) and crushed concrete aggregate (RCA) plus a control section of EW with 20% dune sand (control). Visual inspection after 4 years in service revealed excellent performance with no surface defects or obvious differences between the different sections. The subbase surface was exposed and field-testing using lightweight deflectometer indicated very similar values for the unbound subbases of EW and the control section. The RCA subbase exhibited excellent performance due to self-hardening, providing much higher stiffness than the unbound subbases. The extracted unbound subbase materials satisfied the physical and mechanical requirements of the Qatar Construction Specifications with the exception of liquid limit, plastic limit, and sand equivalent, which are of less significance where the material is placed above the water table. The paper demonstrates that recycled aggregate can perform as well as conventional subbase materials and promotes their wider use to support sustainable development.

**Key words:** alternative aggregates, construction & demolition waste, excavation waste, field investigation, natural resources

## 1. Introduction

The State of Qatar occupies a small peninsula on the south shore of the Arabian Gulf. In common with other states in the region, the construction boom witnessed in Qatar over the past two decades is associated with increased consumption of materials and intensive use of energy. With sustainability being the main factor in the government's 2030 national vision, there is a challenge to balance between development needs and protecting the environment. Qatar lacks quality aggregate, and the construction industry relies mainly on imported aggregate for use in asphalt and concrete. The use of local and recycled materials contributes to sustainable development, with reduced energy

consumption in transporting materials from neighbouring countries as well as minimizing the disposal of construction waste to landfills.

Geologically, Qatar lies on rock that is mostly weak and friable limestone and dolomite, limiting its wider use as aggregate in construction. The strength of local limestone can vary widely with strong bands interbedded with weaker materials [1], and small amounts of the clay mineral attapulgite (palygorsite) in separated bands or disseminated throughout the matrix [2]. A cross section of the excavated limestone in a quarry up to 15 m depth with clay contamination is shown in Fig. 1. Current practice in Qatar is to blend local limestone with 10-20% dune sand to improve its properties and enable compliance with the Qatar Construction Specifications [3]. This material has been successfully used for unbound subbase in road pavement for many years. However, dune sand is not

---

**Corresponding author:** Mohammed bin Saif Al-Kuwari, Dr., Assistant Undersecretary, Director & Senior Engineering Consultant; research areas: environmental and municipal studies. E-mail: khassan@irdme.net.

available in large quantities and the government has recently restricted its use in construction [4].

Construction waste is mainly composed of excavation waste (EW) and construction & demolition waste (CDW) and potentially provides a source of sustainable aggregate supply. In 2010, Qatar generated 12 Mt (million tonnes) of solid waste, including 80% construction waste. In addition, there is approximately 80 Mt of construction waste accumulated in various

landfill sites, with the majority in Rawdat Rashid landfill site [5]. A recent survey by the Planning and Statistics Authority [6] showed a positive reduction in the generation of solid waste to 8.2 Mt in 2017, with 50% construction waste. A recycling target of 20% of the total materials used in construction projects was set in the Qatar Second National Development Strategy by 2022 [7].



**Fig. 1** Limestone quarry with disseminated clay contamination (brown colour) across the excavated face

The use of recycled materials is relatively new in Qatar and hence there is a need to provide evidence-based research on their performance in service. There is very little information available on the field performance of construction materials in Qatar. Field trials are important because they consider the exposure environment in Qatar and the region generally of excessive heat and humidity, aggressive ground conditions, and heavy traffic loading as well as the engineering properties of the materials. This paper presents a field study on the use of recycled materials in road subbase applications by comparing construction data with performance after 4 years in service. It aims to support the government strategy of sustainable development by providing confidence for the wider implementation of recycled materials in construction.

## 2. Construction and Testing of Subbase Road Trials

The access road to Rawdat Rashid, the largest landfill site for construction waste in Qatar was selected for trials. It covers a length of approximately 500 m with heavy traffic loading, in the range of 500-1000 lorries/day, with the existing road suffering from extensive deformation and potholes. The trial was constructed in October 2014 as replacement of the existing access road. Details of the construction data were reported previously [8, 9] and are summarised below. The subbase construction consisted of 3 sections, Fig. 2, each of 120 m length and comprising:

- Section 1: excavation waste (EW) subbase
- Section 2: recycled concrete aggregate (RCA) subbase

- Section 3: a control section made of EW + 20% dune sand

The control section represents the current practice of adding dune sand to local limestone to produce a subbase material to the requirements of the QCS 2014. After removing the existing road and exposing the natural subgrade of limestone, the construction was made in different layers as illustrated in Fig. 3. The new pavement construction consisted of 2 subbase

layers, 150 mm each, with an asphalt overlay of 80 mm. The subbase materials were produced by Lafarge-Qatar, who were managing the Rawdat Rashid landfill site in 2014, by crushing and screening EW and RCA into different sizes. The dune sand was obtained from a nearby deposit in Karaana, managed by the Qatar Primary Materials Company. The subbase materials were mixed and stockpiled near the construction site.

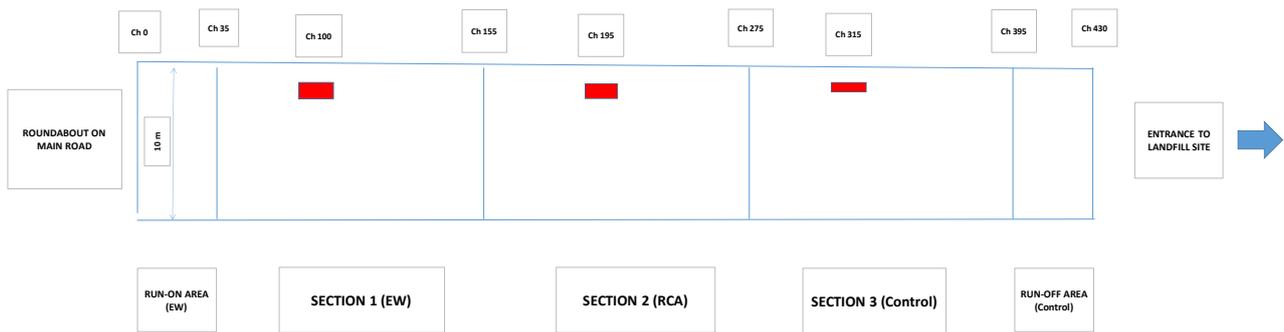


Fig. 2 Layout of the subbase road trials with locations of exposed subbase (not to scale); test sections after 4 years shown in red.

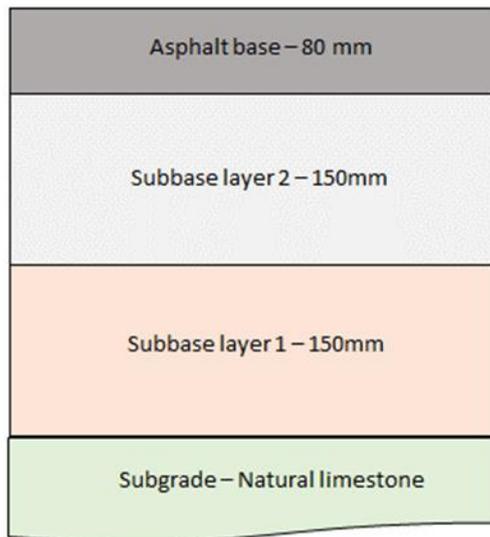


Fig. 3 Cross section of the pavement layers (not to scale).

During construction, the moisture content was adjusted by adding drinking water from a tanker to the stockpile and mixing mechanically with an excavator. The subbase materials were laid using a paver to minimize segregation. Compaction was initially made with 6 passes of a 9-tonne steel wheeled roller followed by 16 passes of a 28-tonne pneumatic tired roller. Further compaction was provided by 6 passes of a

15-tonne steel vibrating roller. Site testing was conducted on the top of compacted subbase layers, with loose samples collected for laboratory testing.

Field-testing of in-situ density, surface modulus and a trafficking trial were carried out on the top of subbase layer 2. The in-situ density was determined using the sand replacement test to BS EN 1997-2 [10] and the trafficking trial according to the procedure described in the UK Specification for Highway Works — Series 800 [11]. Table 1 presents the results of in-situ density and rut depth after trafficking.

The QCS 2014 specified a maximum dry density (MDD) of minimum 2.05 g/cm<sup>3</sup> for unbound subbases, with in place moisture content ±2% of the optimum water content (OWC) and a relative compaction of 100% of the MDD. The results in Table 1 show the three subbase materials satisfied the laboratory MDD, but the field dry density was lower than 100% of the laboratory values. The dry density is dependent on the moisture content, and the hot environment in Qatar caused rapid drying of the materials after compaction as reflected in the field moisture content being on the

lower side of the OWC. However, the laid subbase materials visually appeared well compacted. The trafficking trial provided a further assessment of the subbase materials after being subjected to 1000 equivalent standard axles. The average and maximum

rut depths are shown in Table 1. The average rut depth was less than 10 mm for each subbase section, well below the maximum specified limit of 30 mm in the UK Specification for Highway Works.

**Table 1 In-situ density and rut depths after trafficking.**

Subbase	Laboratory		In-situ density (layer 2)			Rut depth (mm)	
	MDD (g/cm <sup>3</sup> )	OWC (%)	Dry density (g/cm <sup>3</sup> )	MC (%)	Relative compaction (%)	Average	Maximum
EW	2.18	7.1	2.07	5.8	95	7.5	11.0
RCA	2.09	9.2	1.87	8.2	89	7.4	11.0
Control	2.32	5.0	2.12	4.9	91	0.4	6.0
QCS 2014	2.05	± 2%	-	-	100%	-	-

MDD: Maximum Dry Density as per ASTM D1557 [12]

OWC: Optimum Water Content as per ASTM D1557 [12]

To assess the performance of the subbase materials after 4 years in service, small areas of the asphalt overlay were removed to expose the subbase surface. For each road section, an area of 900×1600 mm was exposed from the subbase, highlighted in red in Fig. 2. The asphalt overlay was initially cut into small slabs using a diamond saw, loosened at the edges using a vibrating hammer, and lifted to provide an undisturbed subbase surface. A thin layer of dune sand was sprayed on top of the exposed subbase to provide an even surface for the surface modulus field testing, after which the dune sand was removed and the exposed subbase was loosened using a pick axe and a spade and the loose materials collected in sealed bags for laboratory testing (Fig. 4). The RCA subbase (Section 2) was found to have hardened after 4 years in service and was therefore treated as a bound subbase and cores were extracted for testing as shown in Fig. 5.

### 3. Testing Programme and Results

Testing of the subbase materials was carried out during construction and after 4 years in service. The programme included field and laboratory testing to assess the changes in subbase properties after trafficking in service. The RCA subbase cores after 4 years were tested for compressive strength, moisture

content and density. Details of the testing programme and results are discussed in the following sections.



**Fig. 4 Exposed subbase and sampling of the control unbound materials.**



**Fig. 5 Self-hardened RCA subbase exposed after 4 years in service during coring.**

### 3.1 Visual Inspection


Visual assessment of the road trials was made immediately after construction in November 2014 and periodically every year to October 2018. The access road was heavily trafficked with loaded trucks bringing construction waste into the landfill site and most of the trucks leaving the site loaded with processed recycled materials. The visual inspection showed excellent performance of the road trials in service. No surface defects in the form of cracks, deformation or bleeding were observed on the asphalt overlay, with identical performance between the different sections.

### 3.2 Grading


The QCS 2014 was issued in December 2014, shortly after construction of the trial, and therefore the grading at construction was made to the requirements of the QCS 2010 specification. Three samples were tested for each subbase material and the average grading curves are shown in Fig. 6. All the samples complied with the QCS 2010 grading envelope except the EW subbase, which was slightly coarser between 2 and 5 mm. The effect of adding dune sand on the grading of the control subbase significantly increased the percentage passing at 0.6 mm, but the material remained within the grading limits.

Fig. 7 shows the difference in grading between dune sand and RCA fines (0-5 mm). Whilst the RCA fine aggregate was not used in the field trial to improve the properties of local limestone for subbase applications, it could be used as an alternative to dune sand to achieve compliance with the QCS 2014. The dune sand is almost a single size material with its grading within the narrow range of 0.15 and 0.6mm, hence could not affect the full grading of the subbase material when blended in large quantities. The crushed RCA fines provide a more continuous grading across the different sizes of 0-5 mm, with a relatively high fines content (passing 0.075 mm).

After 4 years in service, the extracted unbound subbase materials (EW and Control) were tested as per

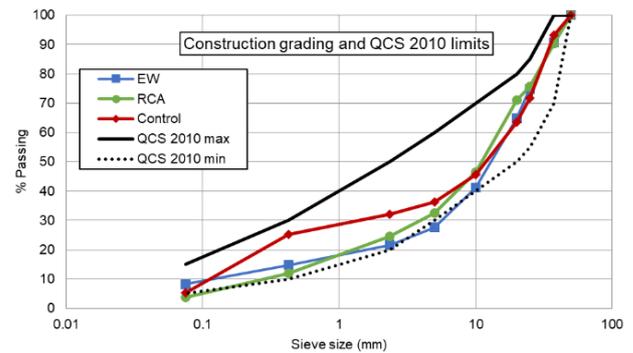

**Fig. 6** Grading of the subbase materials at construction (2014) and QCS 2010 limits.

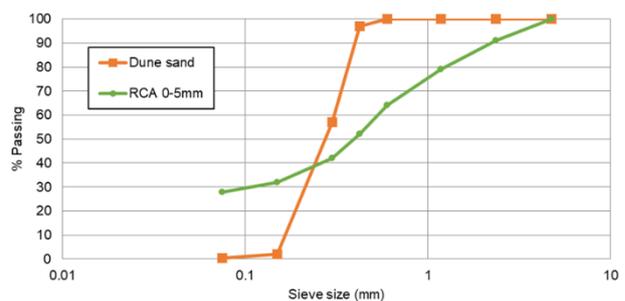

**Fig. 7** Grading of dune sand and RCA fines.

ASTM D6913 [13], following the grading requirements of the QCS 2014 as shown in Fig. 8. The QCS 2014 provides a narrower grading envelope than the QCS 2010 subbase, mainly at the minimum specified limit whereas the maximum limit is almost the same for both specifications. The grading curve for each subbase material represents the average of 3 tested samples. The EW and control showed significantly finer grading than at construction at all sieve sizes. The EW subbase, with its initial coarser grading at construction, remained within the QCS grading envelope with the fine particles of 0.6-0.075 mm towards the higher specified limits. However, the control subbase exceeded the maximum limit between 2 and 0.25 mm, associated with the dune sand addition. The different grading of the unbound materials after 4 years could be attributed to the effect of trafficking but could also be due to the method of extracting the unbound materials causing breakdown of the weak limestone particles, and to the variability of recycled materials.

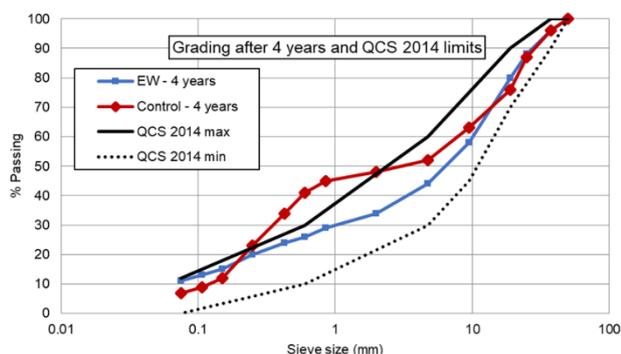


Fig. 8 Grading of the subbase materials after 4 years trafficking and QCS 2014 limits.

3.3 Liquid Limit, Plasticity Index and Sand Equivalent

Table 2 Index tests on the subbase materials at construction and after 4 years in service.

Test/Subbase	At construction			After 4 years			QCS 2014 limits
	EW	RCA	Control	EW	RCA	Control	
Liquid limit (%)	47	47	25	47	-	NP	25 max
Plastic limit (%)	26	NP	NP	27	-	NP	-
Plasticity index (%)	21	NP	NP	20	-	NP	6 max
Sand equivalent	13	34	17	36	-	21	25 min

NP: Non-plastic

After 4 years in service, the EW subbase showed slight changes in the liquid and plastic limits but a significant increase in the sand equivalent to exceed the minimum limit specified in the QCS 2014. A slight increase in the sand equivalent was also observed for the control subbase.

3.4 Physical and Mechanical Properties

Table 3 Physical and mechanical properties of subbase materials.

Test / Subbase	At construction			After 4 years			QCS 2014 limits
	EW	RCA	Control	EW	RCA	Control	
LA abrasion (%)	30	30	28	27	-	27	40 max
Soundness (%)	16.6	2.3	10.6	7.0	-	5.4	20 max-
Soaked CBR (%)	190	145	260	265	-	164	70 min
Swell (%)	0.16	0.17	0.13	0.20	-	0.80	1 max

The surface modulus of the subbase materials was measured using a light weight deflectometer (LWD) in accordance with ASTM E2583 [19]. Six tests were carried out in each subbase section on the top of subbase layer 2 at construction and after 4 years in service. At construction, the measurements were

Liquid limit, plastic limit and plasticity index were tested in accordance with ASTM D4318 [14] and sand equivalent to ASTM D2419 [15]. Table 2 shows the test results of the subbase materials together with the QCS 2014 specified limits. The results show that none of the subbase materials satisfied all the three criteria at construction. The EW subbase failed the QCS 2014 requirements of liquid limit, plasticity index and sand equivalent. The RCA subbase failed the liquid limit but satisfied the plasticity index and sand equivalent requirements. The control subbase passed the liquid limit and plasticity index but failed the sand equivalent.

The results of Los Angeles Abrasion to ASTM C131 [16], soundness to ASTM C 88 [17] after 5 cycles in magnesium sulfate solution, soaked California Bearing Ratio (CBR) to ASTM D1883 [18], and swell to ASTM D1883 [18] are given in Table 3. All the subbase materials comfortably satisfied the requirements of the QCS 2014.

conducted after compaction, before laying the asphalt overlay, at approximately 20 m intervals. After 4 years, the measurements were conducted on the exposed subbase surface (900×1600 mm). The average and minimum modulus values are given in Table 4, together with the Foundation Classes of the UK

pavement design as given in the Interim Advice Note (IAN) 73/06 (20), which was the standard in force at the time the work was carried out.

The LWD values at construction show no significant difference between the three subbase sections with average values ranging between 105 to 109 MN/mm<sup>2</sup>. All the three materials would be a Class 2 Foundation, suitable for traffic loading up to 80 million standard

axles. The exposed subbase after 4 years gave slightly lower values for the unbound materials of 101 and 81 MN/mm<sup>2</sup>, for the EW and control respectively. The RCA subbase would be a Class 3 bound subbase with an average surface modulus exceeding 200 MN/mm<sup>2</sup>. However, it only just exceeds the minimum value for this Class.

**Table 4 LWD values for subbase materials at construction and after 4 years in service.**

Age	Subbase	Average dynamic deflection modulus E <sub>vd</sub> (MN/mm <sup>2</sup> )	Minimum dynamic deflection modulus E <sub>vd</sub> (MN/mm <sup>2</sup> )
At construction	EW	107	70
	RCA	109	87
	Control	105	90
After 4 years in service	EW	101	58
	RCA	205	151
	Control	81	63
Foundation Class 1 (UK guidance)		40	25
Foundation Class 2 (UK guidance)		80	50
Foundation Class 3 (UK guidance)		200	150

### 3.5 RCA Subbase After 4 Years in Service

Cores (150 mm diameter and 150mm height) were extracted from the hardened RCA subbase, Section 2. The cores were sealed in plastic bags and tested in the laboratory for compressive strength as per BS EN 12390-3 [21], density and moisture content. The irregularities at the core ends were minimised by sawing to produce flat perpendicular surfaces. Unbounded metal caps were used for the compressive strength testing as per ASTM C1231 [22], Fig. 9. Three cores were tested for compressive strength in “as-received” conditions, and the crushed cores were dried in an oven at 105±5°C for the moisture content determination. Another set of three cores were used for the density measurement, weight in air and water, and soaked in water for 7 days at 24±5°C. The saturated-surface dry cores were tested for compressive strength for the determination of retained strength as per the QCS 2014.

The results of compressive strength, density and moisture content of the cores are given in Table 5,



**Fig. 9 Compressive strength testing of sled-hardened RCA subbase cores.**

together with the standard deviation and coefficient of variation. The average “as-received” strength of the RCA subbase was 2.3 MPa, and the variation of results was 9%. For the soaked strength, one core was

excluded as it became short after sawing. The average soaked strength of the remaining two cores was 2.2 MPa, with a relatively high variation of 16%. The retained compressive strength, measured as the ratio of soaked to as-received strength, was 96% and exceeded the minimum specified value of 80% in the QCS 2014. The high retained strength indicates high durability for the ingress of water into the pavement. The average

density and moisture content results were 2,124 kg/m<sup>3</sup> and 2.1%, respectively. The hardening of the RCA material, placed and compacted as an unbound subbase like the other sections, is due to the hydration of unhydrated cement particles over time due to moisture added to the fill to bring it to the OWC prior to compaction.

**Table 5 Core results of strength, density and moisture content.**

	Compressive Strength (MPa)		Retained strength (%)	Density (kg/m <sup>3</sup> )	Moisture content (%)
	As received	After soaking			
Core 1	2.1	2.0		2131	1.97
Core 2	2.4	2.5		2149	2.01
Core 3	2.5	-		2092	2.31
Average	2.3	2.2	96%	2124	2.1
SD	0.2	0.4		28.8	0.2
CV %	8.9	15.7		1.4	8.9

#### 4. Discussion of Results

The paper presents a field investigation on the performance of recycled materials in unbound subbase applications after trafficking for 4 years. The assessment was made by comparing the in-service performance with construction data and the QCS 2014, and was based on the recycled materials achieving at least similar performance to the adjacent conventional subbase made with 20% dune sand. Visual inspection revealed excellent performance with no surface defects or cracking of the asphalt overlay, and no obvious differences between the different subbase sections.

The field trial showed that recycled materials satisfied the maximum dry density of the QCS 2014 but failed to achieve the field density of 100% of the maximum dry density achieved in the laboratory. This is attributed to the hot environment in Qatar and its effect on the rapid drying of materials in-situ, making it hard to achieve laboratory values of MDD. Despite the failure in achieving the specified level of density, the subbase materials exhibited excellent performance in the trafficking trial with only minor development of rutting after loading of 1000 ESALs. The average

surface modulus results exceeded 80 MN/mm<sup>2</sup>, with no significant difference between the three subbase sections at construction and after 4 years in service. The surface modulus is a function of the foundation stiffness and thickness of the subbase and the results indicate satisfactory performance under high traffic loading as per the UK Specification for Highway Works. Recycled materials also met comfortably with the QCS 2014 requirements of Los Angeles abrasion, soundness, soaked CBR and swell.

The grading curves of the three subbase materials at construction fell within the grading envelope of the QCS 2010 Class B, except the EW subbase. After 4 years of trafficking, the unbound subbase materials EW and control showed finer grading at all sieve sizes. The control subbase exceeded the maximum specified limits of the QCS 2014 between 0.25-0.2 mm, due to the single-size dune sand grading. The results may indicate the breakdown of the unbound particles under the effect of traffic loadings but could also be attributed to the extraction method of the unbound subbase material and the variability of materials. It is also important to consider the limitation of the small

exposed subbase surface after 4 years compared to the full size of the trials at construction.

The main parameters that failed the QCS 2014 requirements were the index properties of liquid limit, plasticity index and sand equivalent. None of the unbound subbase materials satisfied all the three requirements at construction or after 4 years in service. The addition of 20% dune sand to the control subbase brought the liquid limit and plasticity index into compliance but failed the sand equivalent. The EW subbase failed the liquid limit and plasticity index, but unexpectedly met the sand equivalent requirement. The RCA failed only the liquid limit at construction and hardened with time to become a bound subbase.

There is no doubt the use of dune sand improves the index properties of subbase materials, but the current restriction on its use in construction could widely affect the use of local and recycled limestone materials. The restriction could impose a new threat of the need to import more primary aggregate materials with negative impacts on cost and fuel consumption. RCA fines (0-5 mm) could provide an alternative to dune sand with its more continuous grading and improvement in the plasticity index and sand equivalent properties. They could also lead to self-hardening with enhanced subbase properties. This is an area where further research is required.

As can be seen from Fig. 1, clay is widely disseminated throughout the limestone and it is not possible to separate the clay from the limestone entirely. The clays are highly plastic, so even small amounts of contamination will lead to material failing the current limits for liquid limit, plasticity index and sand equivalent. These index properties are less significant to the pavement performance where the unbound materials are not subjected to water. In a hot and arid environment, such as in Qatar, the unbound materials are generally placed in dry conditions and covered by impermeable asphalt overlay. TRL Overseas Road Note 31 [23] recommends plasticity characteristics for granular subbases in arid and semi-arid climates; the

liquid limit should be less than 55% and the plasticity index less than 20%. The materials used in the trial satisfied these requirements. There could be a potential to revise the QCS requirements to the values proposed by TRL where the unbound materials are placed in a dry environment above the ground water level.

The RCA subbase offered a superior performance with strength gain over time. The RCA material was placed as unbound material and met with all the QCS 2014 requirements with the exception of liquid limit and field density lower than 100% of the maximum dry density. However, the material hardened with time to become a bound subbase and achieved average values of surface modulus just exceeding 200 MN/mm<sup>2</sup> and compressive strength of 2.3 MPa. The hardening of the RCA materials is due to hydration of unreacted cement particles in the RCA in the presence of water [24], as evident from the available moisture content, to become a cement bound material. The weak strength developed by the RCA subbase provides an excellent support to the overlaying pavement and reduces the risk of reflection cracking compared to high strength cement bound materials. To minimize the risk of reflection cracks, Highways England specifies induced cracks for hydraulically bound materials that are expected to reach a compressive strength of  $\geq 10$  MPa at 7 days [25].

While the RCA material could be used at all sizes to produce an alternative subbase material, the fine fraction (0-5 mm) could be blended with local limestone and excavation waste to modify the plasticity criteria instead of dune sand. If RCA fine particles are used to replace dune sand, it is expected to be in the range of 20-30%, leading to a more consistent grading of the subbase material, with potential self-hardening across the subbase layer and enhanced sustainable construction. Further work is required to confirm the practicality of blending RCA fines with limestone aggregate and to optimise the mix design and performance in service.

The road trials clearly demonstrate that recycled materials can perform as well as conventional subbase materials in pavement construction in the arid conditions of Qatar and other areas with similar climate. The results presented in the paper provide practical evidence on the excellent performance of recycled and local materials in service and encourage their wider implementation in practice to support the government strategy of sustainable development.

## 5. Conclusions

The performance of recycled materials in pavement subbase was determined by excavating the asphalt overlay after 4 years in service and comparing field and laboratory results with construction data and the Qatar Construction Specifications (QCS 2014). The road trial proved to be successful, with the subbase materials made of recycled materials of EW and RCA performing at least similar or better than the control subbase made with conventional materials. Visual inspection showed no signs of surface defects or cracking of the asphalt overlay with no difference in appearance between the 3 subbase sections.

A finer grading was found for the unbound subbase after trafficking for 4 years, with the control section made with dune sand falling out of the QCS 2014 specified grading envelope. The subbase materials comfortably met with the key subbase parameters of Los Angeles abrasion, soundness, soaked CBR and swell, with initial satisfactory resistance to rutting and surface modulus under very high traffic loading. However, the unbound subbases did not meet with all the index properties of liquid limit, plasticity index, and sand equivalent, which could be of less significance in the arid climate of Qatar where the material is not subjected to water.

An excellent performance was achieved from the RCA subbase, with the material initially laid as unbound material and hardening with time to provide support to the pavement structure. A further set of construction trials is proposed to investigate the

potential use of RCA fines to replace dune sand to enable the wider utilization of recycled and local materials in construction towards more sustainability in Qatar.

## Acknowledgements

The authors would like to acknowledge the Qatar National Research Fund (QNRF) for funding this project and for the Public Works Authority for site and laboratory testing. Acknowledgement is also extended to the industrial support from Qatar Quarry for supplying the recycled materials for the road construction.

## References

- [1] I. Fourniadis, Geotechnical characterization of the Simsima limestone (Doha, Qatar), in: *Geoenvironmental Engineering and Geotechnics: Progress in Modeling and Applications: Proceedings of Sessions of GeoShanghai*, American Society of Civil Engineers, June 2010, pp. 273-2010.
- [2] H. Holail and S. Al-Hajari, Evidence of an authigenic origin for the palygorskite in a Middle Eocene carbonate sequence from North Qatar, *Qatar University Science Journal* 17 (1997) (2) 405-418.
- [3] QCS, *Qatar Construction Specifications 2014* (5th ed.), Ministry of Municipality & Environment, Qatar Standards. Doha, Qatar, available online at: <https://www.mme.gov.qa/cui/view.dox?id=1441&contentID=3815&siteID=2>.
- [4] Ashghal Technical Note No. 11, Approved fields of using dune sand and how to apply for the required quantities, Public Works Authority, Ashghal, Doha, Qatar, 2019.
- [5] K. E. Hassan, M. S. Al-Kuwari, J. M. Reid, A. Berhane and C. Collis, Developing the use of recycled and secondary aggregate in Qatar, *The International Journal of Pavement Engineering and Asphalt Technology* (PEAT) 14 (2013) (1) 24-46.
- [6] Planning and Statistics Authority, Environment statistics 2019, PSA, Doha, Qatar, available online at: <https://www.psa.gov.qa/en/statistics1/StatisticsSite/LatestStatistics/Pages/Environmental.aspx>.
- [7] Ministry of Development Planning and Statistics, Qatar Second National Development Strategy (2018-2022), 2019, Currently called Planning and Statistics Authority, Doha, Qatar, available online at: <https://www.psa.gov.qa/en/knowledge/Documents/NDS2Final.pdf>.
- [8] K. E. Hassan, J. M. Reid and M. S. Al-Kuwari, *Use of*

*Recycled and Secondary Aggregates in Qatar — Guidance Document*, TRL Published Project Report PPR736, 2015. TRL Limited, Crowthorne, UK.

- [9] J. M. Reid, K. E. Hassan, O. Sirin and R. A. Taha, Demonstrating the worth of recycled aggregates — A case study from Qatar, in: Farid A, Anirban De, Reddy K. R., Yesiller N., and Zekkos D., *Geo-Chicago 2016: Geotechnics for Sustainable Energy*, Chicago-USA.
- [10] BS EN 1997-2, Eurocode 7, Geotechnical design, Ground investigation and testing, British Standards Institution, London, UK, 2007.
- [11] Highways England, UK Specification for Highway Works, *Series 800 Road Pavements – Unbound, cement and other hydraulically bound mixtures*. Manual of Contract Document for Highway Works Volume 1, 2016. London, UK.
- [12] ASTM D1557, Standard test methods for laboratory compaction characteristics of soil using modified effort (56,000 ft-lbf/ft<sup>3</sup> (2,700 kN-m/m<sup>3</sup>)). ASTM International, USA, 2012.
- [13] ASTM D6913/D6913M, Standard test methods for particle-size distribution (gradation) of soils using sieve analysis, ASTM International, USA, 2017.
- [14] ASTM D4318, Standard test methods for liquid limit, plastic limit, and plasticity index of soils, ASTM International, USA, 2017.
- [15] ASTM D2419, Standard test method for sand equivalent value of soils and fine aggregate, ASTM International, USA, 2014.
- [16] ASTM C131/C131M, Standard test method for resistance to degradation of small-size coarse aggregate by abrasion and impact in the Los Angeles Machine, ASTM International, USA, 2014.
- [17] ASTM C88, Standard test method for soundness of aggregates by use of sodium sulfate or magnesium sulfate, ASTM International, USA, 2013.
- [18] ASTM D1883, Standard test method for California Bearing Ratio (CBR) of laboratory-compacted soils, ASTM International, USA, 2016.
- [19] ASTM E2583 – 07, Standard test method for measuring deflections with a light weight deflectometer (LWD), ASTM International, USA, 2015.
- [20] Interim Advice Note 73/06, Design guidance for road pavement foundations (Draft HD25), *Design Manual for Roads and Bridges*, Vol. 7, Part 2, 2009, available online at: [https://www.academia.edu/6406128/INTERIM\\_ADVICE\\_NOTE\\_73\\_06\\_Revision\\_1\\_2009\\_DESIGN\\_GUIDANCE\\_FOR\\_ROAD\\_PAVEMENT\\_FOUNDATIONS\\_DRAFT\\_HD25](https://www.academia.edu/6406128/INTERIM_ADVICE_NOTE_73_06_Revision_1_2009_DESIGN_GUIDANCE_FOR_ROAD_PAVEMENT_FOUNDATIONS_DRAFT_HD25).
- [21] BS EN 12390-3, Testing hardened concrete. Compressive strength of test specimens, British Standards Institution, London, UK, 2009.
- [22] ASTM C1231/C1231M, Standard practice for use of unbonded caps in determination of compressive strength of hardened cylindrical concrete specimens, ASTM International, USA, 2015.
- [23] TRL, A guide to the structural design of bitumen-surfaced roads in tropical and sub-tropical countries, TRL Overseas Road Note 31, TRL Limited, Crowthorne, UK, 1993.
- [24] K. E. Hassan, L. Elghali and C. R. Sowerby, Development of new materials for secondary and recycled aggregates in highway infrastructure, TRL Report 598, TRL Ltd, Crowthorne, UK, 2004.
- [25] Highways England, *Design for new pavement construction*. Design Manual for Roads and Bridges, CD 226, 2020, available online at: <https://www.standardsforhighways.co.uk/prod/attachments/c042429b-a50d-4a4b-bdb7-b49a05213b96?inline=true>.